

# Dual function photocatalysis of cyano-bridged heteronuclear metal complexes for water oxidation and two-electron reduction of dioxygen to produce hydrogen peroxide as a solar fuel

メタデータ	言語: English 出版者: Royal Society of Chemistry 公開日: 2018-04-03 キーワード (Ja): キーワード (En): photocatalysis, hydrogen peroxide, solar fuel 作成者: 荒谷, 悠介, 末延, 知義, 大久保, 敬, 山田, 裕介, 福住, 俊一 メールアドレス: 所属: Osaka University, Japan Science and Technology Agency, Osaka University, Japan Science and Technology Agency, Osaka University, Japan Science and Technology Agency, Osaka City University, Ewha Womans University, Meijo University, Japan Science and Technology Agency
URL	<a href="https://ocu-omu.repo.nii.ac.jp/records/2019716">https://ocu-omu.repo.nii.ac.jp/records/2019716</a>

# Dual function photocatalysis of cyano-bridged heteronuclear metal complexes for water oxidation and two-electron reduction of dioxygen to produce hydrogen peroxide as a solar fuel

Yusuke Aratani, Tomoyoshi Suenobu, Kei Ohkubo, Yusuke Yamada and Shunichi Fukuzumi

<b>Citation</b>	Chemical Communications. 53(24); 3473-3476.
<b>Issue Date</b>	2017-03-25
<b>Type</b>	Journal Article
<b>Textversion</b>	Author
<b>Supplementary files</b>	Supplementary information is available at <a href="https://doi.org/10.1039/C7CC00621G">https://doi.org/10.1039/C7CC00621G</a> .
<b>Rights</b>	The following article appeared in Chemical Communications, 2017, 53, 3473-3476 and may be found at <a href="https://doi.org/10.1039/C7CC00621G">https://doi.org/10.1039/C7CC00621G</a> . This is the accepted manuscript version. Please cite only the published version. この論文は出版社版ではありません。引用の際には出版社版をご確認ご利用ください。
<b>DOI</b>	10.1039/C7CC00621G

Self-Archiving by Author(s)  
Placed on: Osaka City University

## Dual function photocatalysis of cyano-bridged heteronuclear metal complexes for water oxidation and two-electron reduction of dioxygen to produce hydrogen peroxide as a solar fuel

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Yusuke Aratani,<sup>a</sup> Tomoyoshi Suenobu,<sup>a</sup> Kei Ohkubo,<sup>a</sup> Yusuke Yamada<sup>\*b</sup> and Shunichi Fukuzumi<sup>\*cd</sup>

www.rsc.org/

**Photocatalytic production of hydrogen peroxide from water and dioxygen under visible light irradiation was made possible by using polymeric cyano-bridged heteronuclear metal complexes ( $M^{II}[Ru^{II}(CN)_4(bpy)]$ ;  $M^{II} = Ni^{II}, Fe^{II}$  and  $Mn^{II}$ ), where the photocatalytic two-electron reduction of  $O_2$  and water oxidation were catalysed by the Ru and  $M^{II}$  moieties, respectively.**

The production of solar fuel through artificial photosynthesis has attracted considerable attention because of the global energy shortage and growing environmental concerns.<sup>1-3</sup> Artificial photosynthesis is composed of several processes such as light-harvesting, charge-separation, water oxidation and proton or  $CO_2$  reduction, which require hybrid catalytic systems possessing multi-catalytic functions.<sup>4-7</sup> Metal complexes often used as homogeneous catalysts are advantageous for designing and synthesising heteronuclear metal complexes to exhibit the multifunctional catalysis. However, the synthesis of such multifunctional catalysts has been very difficult and the low stability of homogeneous catalysts often causes a problem about truly active species.<sup>8</sup> On the other hand, heterogeneous metal and metal oxide nanoparticles have been extensively studied as robust photocatalysts as well as catalysts for water reduction and oxidation.<sup>9</sup> However, the difficulty to clarify the mechanism of the heterogeneous catalysis has precluded rational design for heterogeneous multifunctional catalysts.<sup>9,10</sup> Recently,

coordination polymers including metal organic frameworks have emerged as a class of heterogeneous catalysts possessing the advantage of homogeneous catalysts.<sup>11</sup> The highly designable nature of the coordination polymers allow to design dual function catalysts used for solar fuel production with energy input from sunlight.<sup>12</sup>

We report herein that polymeric cyano (CN)-bridged heteronuclear metal complexes ( $M^{II}[Ru^{II}(CN)_4(bpy)]$ ;  $M^{II} = Ni^{II}, Fe^{II}$  and  $Mn^{II}$ ) act as dual function catalysts. The catalysts incorporate both a visible-light responsible photosensitiser and catalysis units for photocatalytic reduction of  $O_2$  to  $H_2O_2$  and for  $H_2O$  oxidation.  $H_2O_2$  has merited increasing attention as an ideal solar fuel alternative to gaseous hydrogen, because an aqueous solution of  $H_2O_2$  can be used as a fuel in a one-compartment fuel cell to generate electricity.<sup>13-15</sup> In this context, photocatalytic production of  $H_2O_2$  by reduction of  $O_2$  with water, both of which are earth abundant, has been studied.<sup>16-18</sup> Reported photocatalytic  $H_2O_2$  production systems usually employed a water oxidation catalyst together with a soluble photosensitiser, which also acts as an  $O_2$  reduction catalyst, to utilise visible light efficiently.<sup>18</sup> Incorporation of such a photosensitiser acting as an  $O_2$  reduction catalyst to a water oxidation catalyst can construct efficient photocatalysts by facilitating electron transfer.

$K_2[Ru^{II}(CN)_4(bpy)]$  ( $bpy = 2,2'$ -bipyridine) was synthesised and characterised as reported in the literature.<sup>19</sup> The  $K^+$  ion was replaced by  $Fe^{2+}$  ion to produce  $Fe^{II}[Ru^{II}(CN)_4(bpy)]$ .<sup>20</sup> Similarly  $Ni^{II}[Ru^{II}(CN)_4(bpy)]$ ,  $Mn^{II}[Ru^{II}(CN)_4(bpy)]$ ,  $Co^{II}[Ru^{II}(CN)_4(bpy)]$ ,  $Cu^{II}[Ru^{II}(CN)_4(bpy)]$ ,  $Fe^{II}[Ru^{II}(CN)_4(Me_2phen)]$  and  $Fe^{II}[Ru^{II}(CN)_4\{(MeO)_2bpy\}]$  were synthesised and characterised by powder X-ray diffraction patterns, IR and diffused reflectance UV-vis spectra (see Figs. S1-S3<sup>†</sup>). Powder XRD patterns show that the structure of the complexes is 4,2-ribbon like chain (Fig. 1).<sup>21</sup> IR spectra shifting to higher wavenumber indicate the incorporation of divalent metal ions into the frameworks.  $Fe^{II}[Ru^{II}(CN)_4(bpy)]$  acts as an effective photocatalyst for production of  $H_2O_2$  from  $H_2O$  and  $O_2$  in the presence of  $Sc(NO_3)_3$ , which is expected to enhance  $H_2O_2$  yield by stabilising a reactive intermediate,  $O_2^{\cdot-}$  and thus, by

<sup>a</sup> Department of Material and Life Science, Graduate School of Engineering, Osaka University, SENTAN, Japan Science and Technology Agency (JST), Suita, Osaka 565-0871, Japan.

<sup>b</sup> Department of Applied Chemistry and Bioengineering, Graduate School of Engineering, Osaka City University, Osaka 558-8585, Japan. E-mail: ymd@chem.eng.osaka-cu.ac.jp

<sup>c</sup> Department of Chemistry and Nano Science, Ewha Womans University, Seoul 120-750, Korea. E-mail: fukuzumi@chem.eng.osaka-u.ac.jp

<sup>d</sup> Faculty of Science and Engineering, Meijo University, SENTAN, Japan Science and Technology Agency (JST), Nagoya, Aichi 468-8502, Japan.

<sup>†</sup> Electronic Supplementary Information (ESI) available: Experimental details, Powder XRD (Fig. S1), IR (Fig. S2), DRS (Fig. S3),  $O_2$ -labeling experiment (Figs. S4 and S9), Time course of  $H_2O_2$  generation (Fig. S5), DLS (Fig. S6), EPR (Fig. S7), Emission spectra and Stern-Volmer plots (Fig. S8) and. See DOI: 10.1039/x0xx00000x

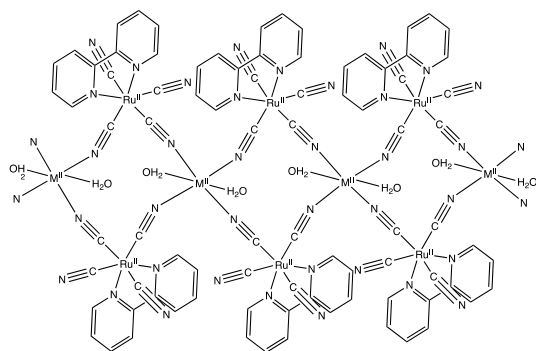


Fig. 1. Schematic drawing of 4,2-ribbon like chain structure.


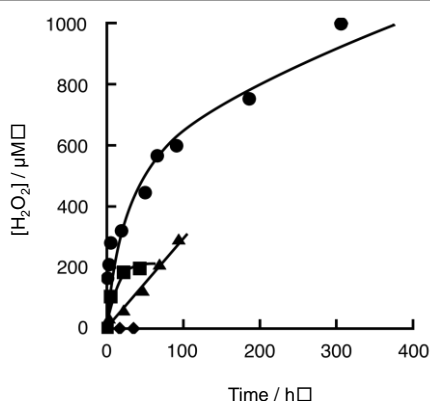


Fig. 2 Time profiles of production of  $\text{H}_2\text{O}_2$  from  $\text{H}_2\text{O}$  and  $\text{O}_2$  with  $\text{Fe}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  (1.2 mM, ●),  $\text{Fe}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{Me}_2\text{phen})]$  (1.1 mM, ■),  $\text{Fe}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4((\text{MeO})_2\text{bpy})]$  (1.0 mM, ▲) and  $\text{Fe}^{\text{II}}_2[\text{Ru}^{\text{II}}(\text{CN})_6]$  (1.4 mM, ◆), in the presence of  $\text{Sc}(\text{NO}_3)_3$  (0.10 M) in  $\text{O}_2$ -saturated  $\text{H}_2\text{O}$  (2.0 mL) under visible light irradiation with a Xenon lamp using a UV cut-off filter ( $\lambda > 390$  nm) at 298 K.

prohibiting back electron transfer,<sup>18a</sup> in  $\text{H}_2\text{O}$  under irradiation of visible light ( $\lambda > 390$  nm) as shown in Fig. 2 [Eq. (1)]. The



origin of oxygen in the produced  $\text{H}_2\text{O}_2$  was confirmed by labelling experiments using gaseous  $^{18}\text{O}_2$  (Fig. S4<sup>†</sup>). It was confirmed that no  $\text{H}_2\text{O}_2$  was produced when  $\text{Fe}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  was replaced by  $\text{Fe}^{\text{II}}_2[\text{Ru}^{\text{II}}(\text{CN})_6]$ , which does not absorb visible light (Fig. 2).<sup>22</sup>

Among various metal-substituted  $\text{M}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$ ,  $\text{Ni}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  exhibited the highest catalytic reactivity for the production of  $\text{H}_2\text{O}_2$  from  $\text{H}_2\text{O}$  and  $\text{O}_2$  as shown in Fig. 3. No  $\text{H}_2\text{O}_2$  formation was observed when  $\text{K}_2[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  was used as a homogeneous catalyst (Fig. S5<sup>†</sup>). The catalytic activity highly influenced by N-bound  $\text{M}^{\text{II}}$  species suggests that  $\text{M}^{\text{II}}$  ions offer the active sites for the photocatalytic water oxidation as reported for conventional Prussian blue analogues used as water oxidation catalysts.<sup>23</sup> Thus, a Ni ion in the 4,2-ribbon like structure may have a coordination structure or bonds with aqua ligands suitable for water oxidation.

When  $\text{H}_2\text{O}$  was replaced by a mixed solvent of  $\text{CH}_3\text{OH}/\text{H}_2\text{O}$  (5:1, v/v), the amount of  $\text{H}_2\text{O}_2$  produced in the photocatalytic

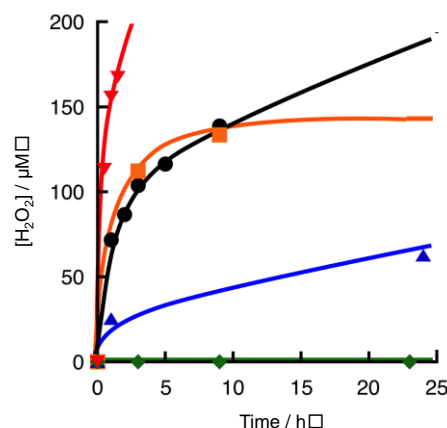


Fig. 3 Time profiles of production of  $\text{H}_2\text{O}_2$  from  $\text{H}_2\text{O}$  and  $\text{O}_2$  with  $\text{M}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  (0.12 mM; M = Ni (▼), Mn (■), Fe (●), Co (▲) and Cu (◆)) in the presence of  $\text{Sc}(\text{NO}_3)_3$  (0.10 M) in  $\text{O}_2$ -saturated  $\text{H}_2\text{O}$  (2.0 mL) under visible light irradiation with a Xenon lamp using a UV cut-off filter ( $\lambda > 390$  nm) at 298 K.

oxidation of  $\text{H}_2\text{O}$  by  $\text{O}_2$  with  $\text{Ni}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  increased significantly as compared with those in only  $\text{H}_2\text{O}$  to afford the apparent turnover number (TON) of 247 based on the number of the monomer unit after 70 h (Fig. 4). The particle sizes of  $\text{Ni}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  have not been significantly changed during the reaction (Fig. S6<sup>†</sup>). The better photocatalytic performance in the mixed solvent than that in pure water can be explained by the lower dielectric constant of the mixed solvent. The lower dielectric constant is beneficial to elongate the lifetime of  $\text{O}_2^{\cdot-}$  by enhancing electrostatic interaction between  $\text{Sc}^{3+}$  and  $\text{O}_2^{\cdot-}$ , resulting in increasing  $\text{H}_2\text{O}_2$  yields. No  $\text{H}_2\text{O}_2$  production in pure  $\text{CH}_3\text{OH}$  as shown in Fig. 4 manifested that water is the electron source of  $\text{O}_2$  reduction.

Nanosecond laser-induced transient absorption spectra of  $\text{K}_2[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  in  $\text{CH}_3\text{OH}/\text{H}_2\text{O}$  (5:1, v/v) were measured for  $[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]^{2-}$  moiety. The lifetime of the excited state of  $[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]^{2-}$  was determined to be 0.23  $\mu\text{s}$  in  $\text{CH}_3\text{OH}/\text{H}_2\text{O}$  (5:1, v/v) (Fig. 5a). The lifetime of the excited state of  $[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]^{2-}$  was shortened by increasing concentration of


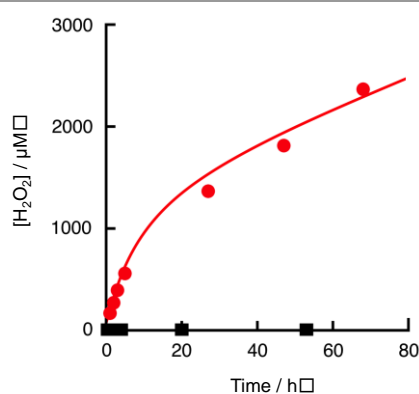



Fig. 4 Time profile of production of  $\text{H}_2\text{O}_2$  from  $\text{H}_2\text{O}$  and  $\text{O}_2$  with  $\text{Ni}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  (9.6 mM) in the presence of  $\text{Sc}(\text{NO}_3)_3$  (67 mM) in  $\text{O}_2$ -saturated  $\text{CH}_3\text{OH}/\text{H}_2\text{O}$  (3.0 mL; 5:1, v/v) under visible light irradiation with a Xenon lamp using a UV cut-off filter ( $\lambda > 390$  nm) at 298 K (●). Time profile in  $\text{CH}_3\text{OH}$  without  $\text{H}_2\text{O}$  under otherwise the same experimental conditions is also shown for comparison (■).

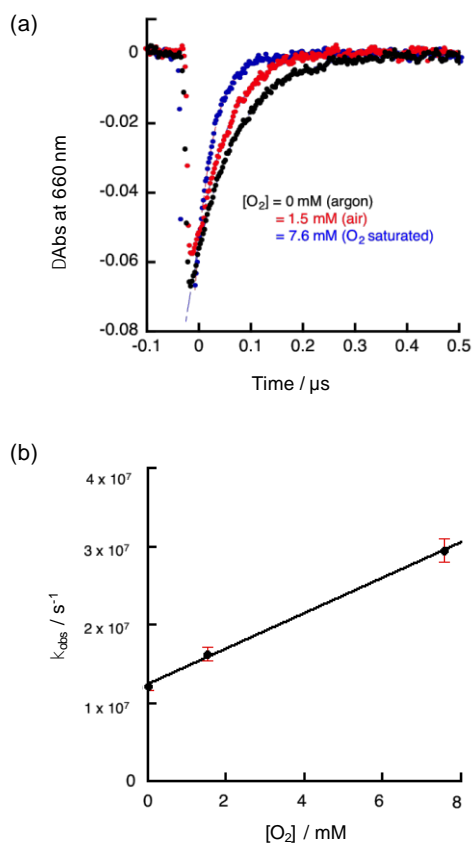


**Fig. 5** (a) Decay time profiles of absorbance at 660 nm observed in CH<sub>3</sub>OH/H<sub>2</sub>O (5:1, v/v) containing K<sub>2</sub>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]<sup>-</sup> (0.29 mM) and various concentrations of O<sub>2</sub> ([O<sub>2</sub>]: 0 (black), 1.5 (red) and 7.6 (blue) mM). (b) Plot of the decay rate constant vs. concentration of O<sub>2</sub>.

O<sub>2</sub> (Fig. 5b). This suggests that electron transfer from the excited state of [Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]<sup>2-</sup> to O<sub>2</sub> occurs to produce [Ru<sup>III</sup>(CN)<sub>4</sub>(bpy)]<sup>+</sup> and O<sub>2</sub><sup>•-</sup>. In the presence of Sc<sup>3+</sup> ions, O<sub>2</sub><sup>•-</sup> is bound to a Sc<sup>3+</sup> ion to afford the O<sub>2</sub><sup>•-</sup>-Sc<sup>3+</sup> complex, which was detected by EPR after photoirradiation of an O<sub>2</sub>-saturated CH<sub>3</sub>OH/H<sub>2</sub>O (5:1, v/v) solution of Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] as shown in Fig. 6 and Fig. S7†, where the superhyperfine due to Sc nucleus (8 lines,  $I = 7/2$ ) is observed.<sup>24</sup> The rate constant of electron transfer from the excited state of [Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]<sup>2-</sup> to O<sub>2</sub> was determined from the linear plot of the decay rate constant vs. concentration of O<sub>2</sub> to be  $2.3(\pm 0.2) \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ , which is diffusion-limited and consists the rate constant of electron transfer determined from a slope of Stern–Volmer plot and the lifetime of [Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]<sup>\*</sup> (Fig. S8†).

The capability of H<sub>2</sub>O oxidation of Ni<sup>II</sup>[Ru<sup>III</sup>(CN)<sub>4</sub>(bpy)]<sup>+</sup> was confirmed in the photocatalytic oxidation of H<sub>2</sub>O by persulphate with Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] in the presence of Sc(NO<sub>3</sub>)<sub>3</sub> in CH<sub>3</sub>OH/H<sub>2</sub>O (5:1, v/v), where O<sub>2</sub> evolution was observed under visible light irradiation ( $\lambda > 390 \text{ nm}$ ). Water oxidation using H<sub>2</sub><sup>18</sup>O instead of H<sub>2</sub><sup>16</sup>O was also conducted to confirm whether evolved oxygen comes from water. After the reaction, the evolved oxygen was analysed by GC-MS (Fig. S9†). The observed O<sub>2</sub> was <sup>18</sup>O<sup>18</sup>O (>99%), indicating that Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] oxidises water even in the presence of

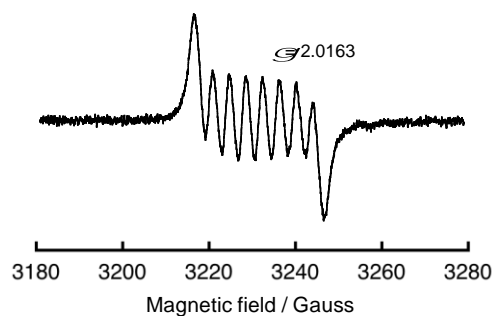

**Fig. 6** EPR spectrum observed under photoirradiation of an O<sub>2</sub>-saturated CH<sub>3</sub>OH/H<sub>2</sub>O (5:1, v/v) solution (2.0 mL) containing Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] (0.50 mM) and Sc(NO<sub>3</sub>)<sub>3</sub> (0.10 M) with an Hg lamp ( $\lambda > 310 \text{ nm}$ ) at 298 K.

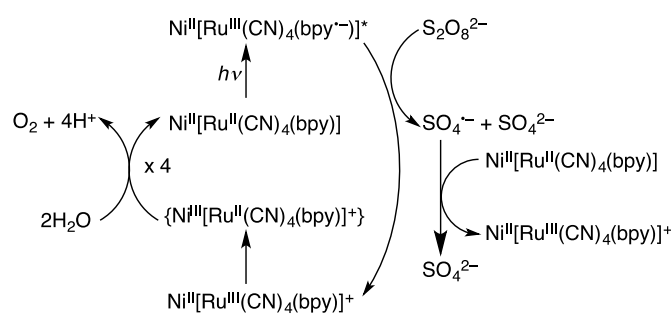


**Scheme 1** Catalytic cycle of visible-light driven water oxidation by persulphate with Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]

methanol. The photocatalytic cycle is given in Scheme 1, where the excited state of Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] was oxidatively quenched by Na<sub>2</sub>S<sub>2</sub>O<sub>8</sub> to produce Ni<sup>II</sup>[Ru<sup>III</sup>(CN)<sub>4</sub>(bpy)]<sup>+</sup> and, then, {Ni<sup>II</sup>[Ru<sup>III</sup>(CN)<sub>4</sub>(bpy)]<sup>+</sup> that oxidises water to evolve O<sub>2</sub>.

The mechanism of photocatalytic production of H<sub>2</sub>O<sub>2</sub> from H<sub>2</sub>O and O<sub>2</sub> with Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] in the presence of Sc<sup>3+</sup> is shown in Scheme 2. Photoexcitation of Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] resulted in electron transfer from the excited state of Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] to O<sub>2</sub> in the presence of Sc<sup>3+</sup> to produce Ni<sup>II</sup>[Ru<sup>III</sup>(CN)<sub>4</sub>(bpy)]<sup>+</sup> and O<sub>2</sub><sup>•-</sup>-Sc<sup>3+</sup>. The O<sub>2</sub><sup>•-</sup>-Sc<sup>3+</sup> complex disproportionates in the presence of H<sup>+</sup> to produce H<sub>2</sub>O<sub>2</sub>.<sup>12</sup> On the other hand, four equivalents of Ni<sup>II</sup>[Ru<sup>III</sup>(CN)<sub>4</sub>(bpy)]<sup>+</sup> oxidises water to produce O<sub>2</sub> and four equivalents of H<sup>+</sup>.

In conclusion, polymeric cyano-bridged heteronuclear metal complexes (M<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]<sub>n</sub>; M<sup>II</sup> = Ni<sup>II</sup>, Fe<sup>II</sup> and Mn<sup>II</sup>) exhibited dual function photocatalysis for H<sub>2</sub>O oxidation and O<sub>2</sub> reduction to H<sub>2</sub>O<sub>2</sub> in photocatalytic production of H<sub>2</sub>O<sub>2</sub> from H<sub>2</sub>O and O<sub>2</sub>. The highest apparent TON of 247 based on the number of monomer unit was obtained with Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)] for production of H<sub>2</sub>O<sub>2</sub> from H<sub>2</sub>O and O<sub>2</sub> in

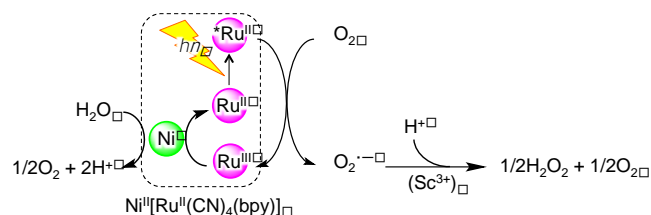

**Scheme 2** Catalytic cycle of visible-light driven water oxidation by O<sub>2</sub> with Ni<sup>II</sup>[Ru<sup>II</sup>(CN)<sub>4</sub>(bpy)]

the presence of  $\text{Sc}(\text{NO}_3)_3$  in  $\text{CH}_3\text{OH}/\text{H}_2\text{O}$  (5:1, v/v) under visible light irradiation ( $\lambda > 390$  nm). The dual function photocatalysis of  $\text{M}^{\text{II}}[\text{Ru}^{\text{II}}(\text{CN})_4(\text{bpy})]$  in a single catalyst provides a very efficient integrated process for the photocatalytic production of  $\text{H}_2\text{O}_2$  as a promising solar fuel from  $\text{H}_2\text{O}$  and  $\text{O}_2$  using solar energy.

## Acknowledgements

The authors acknowledge Dr. Tatsuo Nakagawa for transient absorption spectra measurements. This work was supported by the SENTAN project from Japan Science Technology Agency (JST) to S.F., Grants-in-Aid (no. 16H02268 to S.F., no. 15K14223 to Y.Y.) for Scientific Research from Japan Society for the Promotion of Science (JSPS) and ENEOS hydrogen trust fund to Y. Y.

## Notes and References

- (a) G. L. Ashford, M. K. Gish, A. K. Vannucci, M. K. Brennaman, J. L. Templeton, J. M. Papanikolas and T. J. Meyer, *Chem. Rev.*, 2015, **115**, 13006-13049; (b) T. R. Cook, D. K. Dogutan, S. Y. Reece, Y. Surendranath, T. S. Teets and D. G. Nocera, *Chem. Rev.*, 2010, **110**, 6474-6502.
- N. Armaroli and V. Balzani, *Chem.–Eur. J.*, 2016, **22**, 32-57.
- (a) T. A. Faunce, W. Lubitz, A. W. Rutherford, D. MacFarlane, G. F. Moore, P. Yang, D. G. Nocera, T. A. Moore, D. H. Gregory, S. Fukuzumi, K. B. Yoon, F. A. Armstrong, M. R. Wasielewski and S. Styring, *Energy Environ. Sci.*, 2013, **6**, 695-698; (b) E. W. McFarland, *Energy Environ. Sci.*, 2014, **7**, 846-854.
- (a) S. Fukuzumi, K. Ohkubo and T. Suenobu, *Acc. Chem. Res.*, 2014, **47**, 1455-1464; (b) S. Fukuzumi, *Curr. Opin. Chem. Biol.*, 2015, **25**, 18-26; (c) S. Fukuzumi, *Eur. J. Inorg. Chem.*, 2008, **9**, 1351-1362.
- (a) D. Kim, K. K. Sakimoto, D. Hong and P. Yang, *Angew. Chem. Int. Ed.*, 2015, **54**, 3259-3266; (b) S. Fukuzumi, D. Hong and Y. Yamada, *J. Phys. Chem. Lett.*, 2013, **4**, 3458-3467.
- (a) S. Berardi, S. Drouet, L. Francàs, C. Gimbert-Suriñach, M. Guttentag, C. Richmond, T. Stolla and A. Llobet, *Chem. Soc. Rev.*, 2014, **43**, 7501-7519; (b) L. Duan, L. Wang, F. Li, F. Li and L. Sun, *Acc. Chem. Res.*, 2015, **48**, 2084-2096.
- Y. Yamazaki, H. Takeda and O. Ishitani, *J. Photochem. Photobiol. C, Photochem. Rev.*, 2015, **25**, 106-137.
- (a) V. Artero and M. Fontecave, *Chem. Soc. Rev.*, 2013, **42**, 2338-2356; (b) S. Fukuzumi and D. Hong, *Eur. J. Inorg. Chem.*, 2014, **2014**, 645-659; (c) X. Wu, F. Li, B. Zhang and L. Sun, *J. Photochem. Photobiol. C: Photochem. Rev.*, 2015, **25**, 71-89; (d) J. J. Stracke and R. G. Finke, *ACS Catal.*, 2014, **4**, 909-933.
- (a) T. Zhang and W. Lin, *Chem. Soc. Rev.*, 2014, **43**, 5982-5993; (b) X. Zou and Y. Zhang, *Chem. Soc. Rev.*, 2015, **44**, 5148-5180; (c) J. Ran, J. Zhang, J. Yu, M. Jaroniec and S. Z. Qiao, *Chem. Soc. Rev.*, 2014, **43**, 7787-7812.
- (a) A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253-278; (b) T. Hisatomi, J. Kubota and K. Domen, *Chem. Soc. Rev.*, 2014, **43**, 7520-7535; (c) D. M. Fabian, S. Hu, N. Singh, F. A. Houle, T. Hisatomi, K. Domen, F. E. Osterloh and S. Ardo, *Energy Environ. Sci.*, 2015, **8**, 2825-2850.
- (a) A. H. Chughtai, N. Ahmad, H. A. Younus, A. Laypkov and F. Verpoort, *Chem. Soc. Rev.*, 2015, **44**, 6804-6849; (b) Q.-L. Zhu and Q. Xu, *Chem. Soc. Rev.*, 2014, **43**, 5468-5512; (c) M. Ranocchiarri and J. A. van Bokhoven, *Phys. Chem. Chem. Phys.*, 2011, **13**, 6388-6396; (d) P. Kaur, J. T. Hupp and S. B. T. Nguyen, *ACS Catal.*, 2011, **1**, 819-835; (e) A. Corma, H. García, and F. X. Llabrés i Xamena, *Chem. Rev.*, 2010, **110**, 4606-4655.
- (a) T. Zhang and W. Lin, *Chem. Soc. Rev.*, 2014, **43**, 5982-5993; (b) C. Wang, K. E. deKrafft and W. Lin, *J. Am. Chem. Soc.*, 2012, **134**, 7211-7214; (c) Y. Horiuchi, T. Toyao, M. Saito, K. Mochizuki, M. Iwata, H. Higashimura, M. Anpo and M. Matsuoka, *J. Phys. Chem. C*, 2012, **116**, 20848-20853; (d) T. Toyao, M. Saito, S. Dohshi, K. Mochizuki, M. Iwata, H. Higashimura, Y. Horiuchi and M. Matsuoka, *Chem. Commun.*, 2014, **50**, 6779-6781.
- (a) S. Fukuzumi, *S. Biochim. Biophys. Acta*, 2016, **1857**, 604-611; (b) S. Fukuzumi, Y. Yamada and K. D. Karlin, *Electrochim. Acta*, 2012, **82**, 493-511; (c) S. Fukuzumi and Y. Yamada, *Aust. J. Chem.*, 2014, **67**, 354-364; (d) L. An, T. Zhao, X. Yan, X. Zhou and P. Tan, *Sci. Bull.*, 2015, **60**, 55-64.
- (a) H. Zhuang, L. Yang, J. Xu, F. Li, Z. Zhang, H. Lin, J. Long and X. Wang, *Sci. Report*, 2015, **5**, 16947-16954; (b) N. Kaynan, B. A. Berke, O. Hazut and R. Yerushalmi, *J. Mater. Chem. A*, 2014, **2**, 13822-13826.
- (a) Y. Yamada, S. Yoshida, T. Honda and S. Fukuzumi, *Energy Environ. Sci.*, 2011, **4**, 2822-2825; (b) S. A. M. Shaegh, N. T. Nguyen, S. M. M. Ehteshami and S. H. A. Chan, *Energy Environ. Sci.*, 2012, **5**, 8225-8228; (c) Y. Yamada, M. Yoneda, and S. Fukuzumi, *Chem.–Eur. J.*, 2013, **19**, 11733-11741; (d) Y. Yamada, M. Yoneda and S. Fukuzumi, *Inorg. Chem.*, 2014, **53**, 1272-1274; (e) Y. Yamada, M. Yoneda and S. Fukuzumi, *Energy Environ. Sci.*, 2015, **8**, 1698-1701.
- (a) K. Mase, M. Yoneda, Y. Yamada and S. Fukuzumi, *Nat. Commun.*, 2016, **7**, 11470; (b) K. Mase, M. Yoneda, Y. Yamada and S. Fukuzumi, *ACS Energy Lett.*, 2016, **1**, 913-919; (c) S. Fukuzumi and Y. Yamada, *ChemElectroChem*, 2016, **3**, 1978-1989.
- (a) Y. Shiraishi, Y. Kofuji, H. Sakamoto, S. Tanaka, S. Ichikawa and T. Hirai, *ACS Catal.*, 2015, **5**, 3058-3066; (b) Y. Shiraishi, S. Kanazawa, Y. Kofuji, H. Sakamoto, S. Ichikawa, S. Tanaka and T. Hirai, *Angew. Chem., Int. Ed.*, 2014, **53**, 13454-13459.
- (a) S. Kato, J. Jung, T. Suenobu and S. Fukuzumi, *Energy Environ. Sci.*, 2013, **6**, 3756-3764; (b) Y. Isaka, S. Kato, D. Hong, T. Suenobu, Y. Yamada and S. Fukuzumi, *J. Mater. Chem. A*, 2015, **3**, 12404-12412; (c) Y. Isaka, S. Kato, D. Hong, T. Suenobu, Y. Yamada and S. Fukuzumi, *Catal. Sci. Technol.*, 2016, **6**, 681-684.
- (a) C. A. Bignozzi, C. Chiorboli, M. T. Indelli, M. A. R. Scandola, G. Varani and F. Scandola, *J. Am. Chem. Soc.*, 1986, **108**, 7872-7873; (b) J. L. Habib Jiwan, B. Wegewijs, M. T. Indelli, F. Scandola and S. E. Braslavsky, *Recl. Trav. Chim. Pays-Bas*, 1995, **114**, 542-549.
- M. D. Ward, *Dalton Trans.*, 2010, **39**, 8851-8867.
- (a) Y.-H. Li, W.-R. He, X.-H. Ding, S. Wang, L.-F. Cui and W. Huang, *Coord. Chem. Rev.*, 2012, **256**, 2795-2815; (b) L. M. Toma, R. Lescouëzec, S. Uriel, R. Llusar, C. Ruiz-Pérez, J. Vaissermann, F. Lloret and M. Julve, *Dalton Trans.*, 2007, 3690-3698; (c) J. Xia, W. Shi, X.-Y. Chen, H.-S. Wang, P. Cheng, D.-Z. Liao and S.-P. Yan, *Dalton Trans.*, 2007, 2373-2375.
- Y. Aratani, K. Oyama, T. Suenobu, Y. Yamada and S. Fukuzumi, *Inorg. Chem.*, 2016, **55**, 5780-5786.
- (a) Y. Yamada, K. Oyama, R. Gates and S. Fukuzumi, *Angew. Chem. Int. Ed.*, 2015, **54**, 5613-5617; (b) Y. Isaka, K. Oyama, Y. Yamada, T. Suenobu and S. Fukuzumi, *Catal. Sci. Technol.*, 2016, **6**, 681-684.
- S. Fukuzumi, M. Patz, T. Suenobu, Y. Kuwahara and S. Itoh, *J. Am. Chem. Soc.*, 1999, **121**, 1605-1606.